


MIST + FULL COAT ON ZINGA

Information given in this document should be used in complement with technical specifications given in the technical data sheet of ZINGA.


PROBLEM - BUBBLING

When applying topcoats directly on ZINGA, a problem of bubbling may occur. Where the finish coat is strong and flexible enough, some of these bubbles may not break as the finish coat dries. They remain in the dry film, perhaps collapsing against the primer in a crater-like defect. Where they do break, there may be insufficient flow left in the drying film to allow the sites to heal, and pinholes will remain in the film. In aggressive environments, the unprotected ZINGA at the base of such pinholes may become a weak spot of the system (though it will provide cathodic protection, the localised spot will deplete fast), although little effect will be encountered in less extreme environments.

Bubbling is directly related to ZINGA's morphology. ZINGA is very porous, due to its high PVC/CPVC ratio (Pigment Volume Concentration / Critical Pigment Volume Concentration).

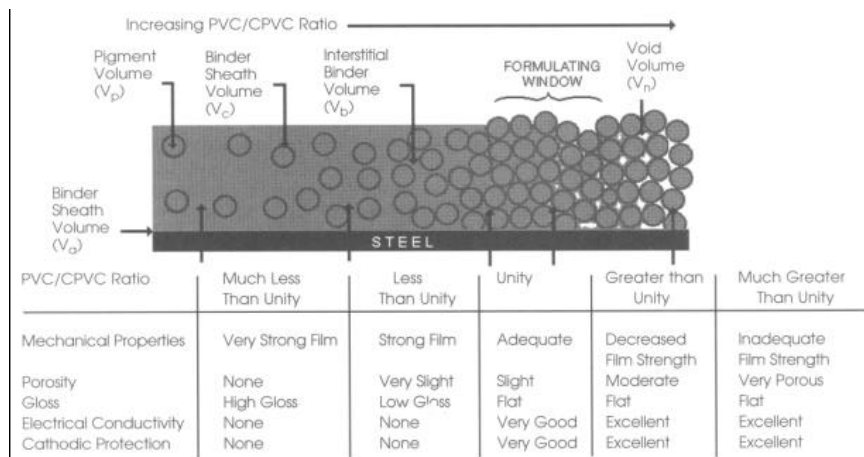


Initially, the interstitial voids in ZINGA are filled with air. As the newly applied finish is applied over ZINGA, the binder from the topcoat penetrates the ZINGA porosities and displaces air. This air must pass out through the topcoat into the environment. The release of air during the final stages of setup may be delayed by virtue of the high viscosity, fast setup, skinning, or pigmentation of the finish. This occluded air may locally push the finish out from ZINGA in a dry blister or bubble as it tries to escape. In the early stages of drying, the blisters or bubbles may break, releasing the air. But when the critical balance between the rheological force and the surface tension force in the topcoat shift during drying in favour of the rheological force, such release may become impossible.

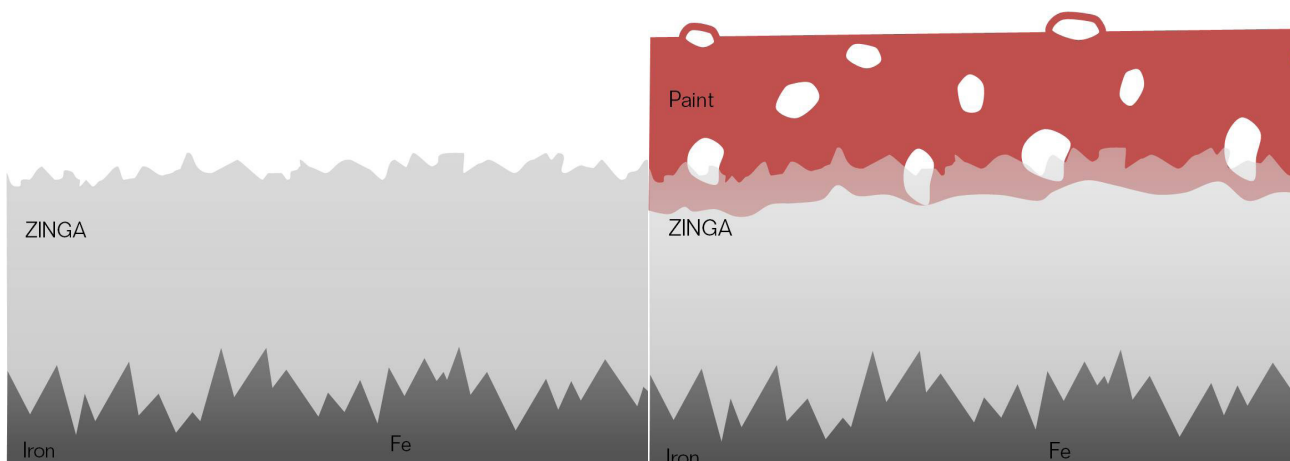

SOLUTION - MIST/FULL COAT TECHNIQUE

A thin coat of sealer or topcoat is applied over the surface of ZINGA before a full pass of the coating at the normal film thickness. This thin film penetrates only the surface layers of the ZINGA and seals its surface. Also relatively porous, the mist coat presents little obstacle to the passage of air from these upper layers.

First, a thin continuous layer is applied which gives air bubbles easy passage through the film. The first mist coat also provides a barrier for aggressive solvents in the topcoat.

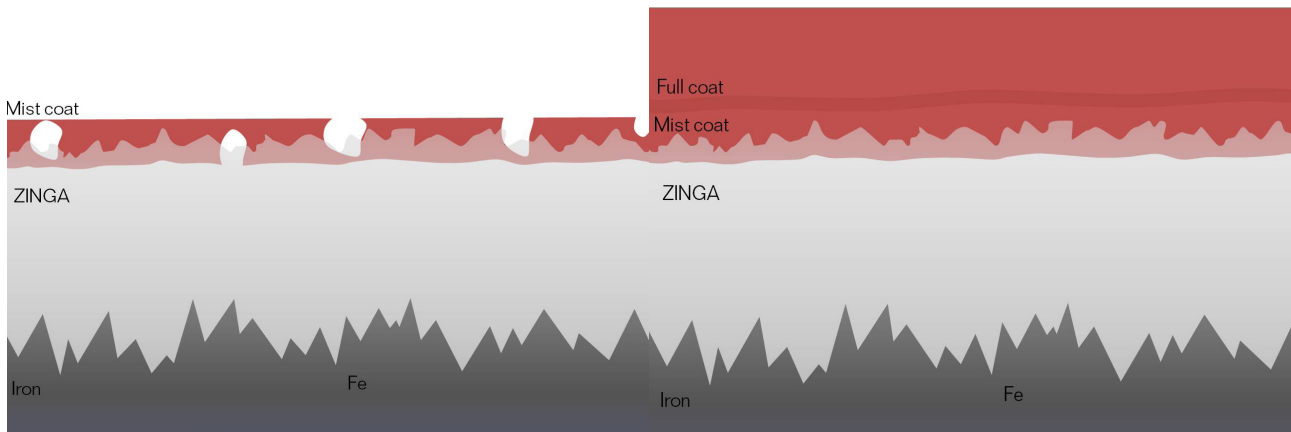

Mist coat:

Application at least 6 hours after ZINGA is touch-dry.
25 to 30 μm DFT (**continuous** layer).
Normal dilution according to the technical data sheet.

Full coat:

Application at least 2 hours after the mist coat is touch-dry.
Specified layer thickness minus 25 to 30 μm DFT (of mist coat).
Normal dilution according to the technical data sheet.

The information on this sheet is merely indicative and is given to the best of our knowledge based on practical experience and testing. The conditions or methods of handling, storage, use or disposal of the product cannot be controlled by us and are therefore outside our responsibility. For these and other reasons we retain no liability in case of loss, damage or costs that are caused by or that are linked in any way to the handling, storage, use or disposal of the product. Any claim concerning deficiencies must be made within 3 months upon reception of the goods quoting the relevant batch number. We retain the right to change the formula if properties of the raw material are changed. This data sheet replaces all former specimens.